

*Hydrothermal synthesis of nanostructured inorganic powders
by a continuous process under supercritical conditions...*

N. MILLOT, B. XIN, C. PIGHINI, D. AYMES

LRRS, UMR 5613 CNRS/Université de Bourgogne, BP 47870, 21078 DIJON Cedex, France

Abstract :

In this study, using a prototype of hydrothermal synthesis in subcritical and supercritical water working in a continuous way, nanometric ceramic precursors with perfectly defined composition are produced: spinel ferrites such Fe_2CoO_4 , TiO_2 with anatase structure and also perovskite structures such as BaZrO_3 . The as-prepared powders are fully characterized by complementary experiments: X-ray diffraction, electron microscopies, EDX spectrometry, surface area measurement... Thus, particles size, morphology, aggregation state, crystal structure, composition are investigated. Moreover, magnetic properties of the ferrites products are studied. The powders obtained are pure phases very well crystallized in a nanometric range.

Keywords : Powders-chemical preparation, Grain size, Ferrites, Perovskites, TiO_2

1. Introduction

Nanostructured ceramic materials for electronic applications draw industry and scientist attention because of their physical properties depending on grain size [

i]. Since surface energy allows stabilizing highly symmetrical phases apart from the usual limits, new materials can be obtained [ii]. Then, synthesis methods of nanometric powders are very interesting. In preliminary works about ferrites obtained by both soft chemistry and mechanosynthesis, our research group present three original approaches: i) control of grain size and morphologies of these nanograined powders is possible by adaptation of the synthesis route [iii]; ii) getting simultaneously homogeneity in both morphological and chemical properties is a challenge in nano-chemistry [iv]; iii) surface energy, which allows to stabilize highly symmetrical phases apart from the usual limits, leads to new materials [2, v-vi]. Nevertheless, soft chemistry technologies do not allow having a huge production and cannot be developed at industrial level. Continuous synthesis technologies, allowing several tens grams per hour production, are then very interesting. In this perspective, a continuous production prototype of hydrothermal synthesis in subcritical and supercritical water has been developed [vii]. Recent papers [viii-ix] summarize the specific features of supercritical fluid processes for material synthesis and processing. The mechanism of nanoparticle formation has been discussed with emphasis on the solubility of the metal oxide and kinetics of the hydrothermal synthesis, both of which significantly vary around the critical point due to the change of properties of water. Synthesized oxide powders in supercritical water have revealed three interesting qualities: they can have nanometric grain size with control particle morphology, they are very well crystallized and they have clean surface grains. Then, the two aims of this new study are both to illustrate these particularities and to show the versatility of supercritical media by producing three different oxides very interesting for their potential applications: Fe_2CoO_4 (spinel), BaZrO_3 (perovskite) and TiO_2 (anatase). These syntheses are original because of both the purity of the crystalline phase obtained and the very low size of the grains. Furthermore, the originality of the prototype device developed in this study is to allow huge production thanks to a continuous process.

2. Experimental procedure

The synthesis conditions are described in table 1 and the experimental apparatus used for these hydrothermal synthesis (in sub or supercritical conditions) is described in others publications [7, 9, x]. The metal salt aqueous solution is prepared and fed into the apparatus in one stream. In another stream, distilled water is pressurized and then heated to a temperature that is above the temperature desired. The pressurized metal salt solution stream and the pure supercritical water stream (eventually a basic solution is fed in a third way) are combined in a mixing point just before the reactor, which leads to rapid heating and subsequent reaction in the reactor. The pump flows are given here only for the BaZrO₃ synthesis: cationic solutions 8.1 mL/mn; water 29.5 mL/mn; basic solution 12.4 mL/mn. The residence time of the solution in the reactor is of 10 s in most of the experiments (the reactor is an Inconel serpentine with a length of 2 m and a diameter of 2.3 mm). After the reactor, the solution is rapidly quenched and filters remove agglomerated particles. Then, the suspension obtained is centrifuged and washed with deionized water under ultrasonication for 5 min. After about 10 washings the centrifugation is not possible, a sol is formed which is freeze-dried.

Surface area measurements are performed using AUTOSORB apparatus with N₂ adsorbing gas. Samples (150-200 mg of powder) are outgassed at 493 K. The B.E.T. method is used in calculation of surface area values from the isotherm of nitrogen adsorption.

Powders are all characterized by X-ray diffraction (XRD) using a Siemens D5000 automatic powder diffractometer, operating at 35 mA and 50 kV (the radiation used is precise table 2). Correction for instrumental broadening is determined from a standard reference material, annealed BaF₂. Pseudo-Voigt peak profile analysis, using the Langford method [xi], is performed to determine both the average crystallite size (size of a region over which the diffraction is coherent) and crystallographic imperfections (microdistorsions, stacking faults

...). The lattice parameters of the powders are deduced from XRD line positions using a least-squares refinement method⁽¹⁾.

The mean particle diameter is inferred from Scanning Electron Micrographs (SEM)(JEOL JSM-6400F). Microstructural observations are performed with a 2010 FEG-TEM for high-resolution imaging with a practical resolution of 0.19 nm. Chemical composition is determined by EDXS with a LINK OXFORD Energy Dispersive X-ray analyser.

The hysteresis loops of samples are measured with a M2100 50 Hz hysteresometer.

3. Results and discussion

Bis(ammonium lactate)titanium dihydroxide (ALT) is hydrolysed at a temperature of 300°C under 300 bar (table 1). As seen in figure 1a, pure anatase form is obtained. All the reflections of the TiO₂ pattern are not labeled because some of them are mixed due to their very large widths. This width is significant of a very small crystallites size which is also proved by high specific surface (255 m²/g, table 2). The Langford method leads to a crystallite size of about 3 nm. The narrow size distribution of the grains is attested by TEM micrographs and low frequency Raman scattering measurements of the nanoparticles vibration eigenmodes (study in progress). The advantages of this new synthesis is to allow huge production (several tens grams per hour) contrary to a precedent study where the hydrolysis of the ALT precursor has been realized in sealed glass ampoules [xii]. Moreover, the powders obtained in our study have smaller size: 3 nm at 300°C contrary to the 16 nm obtained by Möckel & al. at the same temperature [12].

Fe₂CoO₄ powder is very well dispersed and homogeneous with a grain size of about 3 nm deduced from XRD results. This value matches quite well the average particle diameter

⁽¹⁾ In-house software taking into account the effect of sample gap.

deduced from specific area measurements ($S_{\text{BET}} = 236 \text{ m}^2 \cdot \text{g}^{-1}$ which yields a diameter of 4.8 nm). The grain size distribution is quite narrow, even after the thermal annealing (fig. 2a). This treatment leads to a grain size increase: $\Phi_{\text{XRD}} = 34 \text{ nm}$. Nevertheless, smaller grain appears in HRTEM image (fig 2b) of about 7 nm. The lattice parameters of this Fe_2CoO_4 spinel phase is $a_{\text{exp}} = 8.3839 \pm 0.0001 \text{ \AA}$. This is to be compared with the value reported in literature $a_{\text{lit}} = 8.35 \pm 0.01 \text{ \AA}$ for a powder obtained by soft chemistry and heated at 500°C [xiii]. The calculated value $a_{\text{cal}} = 8.3878 \text{ \AA}$ by the Poix method is in relatively good agreement with the experimental one (the cation-oxygen distances used for the calculation of the lattice parameter are given in the reference [xiv]). The difference could be explained by a possible oxidation of the cobalt cation in Co^{3+} (2.4% in order to obtain the experimental value). It can not be explained by a redistribution of the cobalt cation in tetrahedral coordination, phenomenon which increases the lattice parameter (8.4099 \AA if all the Co^{2+} are in tetrahedral coordination). The coercive field of the freeze-dried powder is about 3730 Oe at 77 K (the powder has a superparamagnetic behavior at ambient temperature). The coercive field of the powder obtained after the thermal annealing is higher: 7350 Oe at 77 K (1180 Oe at ambient temperature). These higher values are due to the bigger particle size of the annealed powder. This powder could be a good candidate for magnetic recording.

For the first time a BaZrO_3 nanometric powder is obtained by an hydrothermal synthesis. Indeed, in a recent study, Kolenko & al. have obtained nanocrystalline ZrO_2 (8-12 nm), amorphous $\text{ZrO}(\text{OH})_2$ or microcrystalline BaZrO_3 (2-5 μm) powders, depending of the synthesis conditions [xv]. Powder is very well dispersed with a grain size of about 74 nm deduced from XRD results. The lattice parameters of this perovskite phase is $a_{\text{exp}} = 4.198 \pm 0.001 \text{ \AA}$. This is to be compared with the value reported in the 6-399 ICDD card $a_{\text{ICDD}} = 4.193 \text{ \AA}$. In the XRD pattern of the figure 1b, the reflections not labeled are those of BaCO_3 . This

parasite phase appears when the suspension is in contact with air and can be eliminated after an appropriate washing with diluted acetic acid. This BaZrO₃ nanometric powder obtained in this study may reveal a smaller sintering temperature than micrometric grains and could be interesting in aero-space and related industries or to made crucibles for growing high-quality high temperature superconductors single crystals (study in progress) [xvi].

4. Conclusion

Nanocrystalline Fe₂CoO₄ is synthesized in the spinel structure with very small grain size (about 3 nm). After an annealing at 600°C, the grain size is always in a nanometric range (34 nm) and the cationic distribution is determined precisely thanks to the Poix method. The coercive field of this latest powder is very high (7350 Oe at 77 K). TiO₂ pure anatase is also obtained with a narrow size distribution of about 3 nm. Nanometric BaZrO₃ perovskite composition is prepared. Our technology has the main advantages to be easy to use compared to closed reactors and to have a high productivity. It opens news insights into the decrease of the sintering temperature of such interesting ceramic product.

Table 1

Synthesis conditions of TiO_2 , BaZrO_3 and Fe_2CoO_4 .

Table 2

Specific area measurements and X-ray diffraction analysis of TiO_2 , BaZrO_3 and Fe_2CoO_4 powders. The XRD line profile analysis is performed according to Halder & Wagner method. Due to very large diffraction peaks, the lattice parameter cannot be determined with precision for both TiO_2 and Fe_2CoO_4 powders obtained just after the thermohydrolysis.

Fig. 1

X-ray diffractograms of a) TiO_2 , b) BaZrO_3 , c) Fe_2CoO_4 powders obtained just after the freeze-dried process; d) Fe_2CoO_4 obtained after a thermal annealing of 4 hours at 600°C under air atmosphere. a), c) and d) XRD patterns are obtained with $\text{Cu K}\beta$ radiation and b) is obtained with $\text{Co K}\alpha_1$ radiation. All the reflections of the TiO_2 pattern are not labeled because some of them are mixed due to their very large widths. In the b) XRD pattern, reflections not labeled are those of BaCO_3 . This parasite phase appears when the suspension is in contact with air and can be eliminated after an appropriate washing with diluted acetic acid.

Fig. 2



a) SEM micrograph; b) HRTEM micrograph of Fe_2CoO_4 obtained by thermohydrolysis in the supercritical conditions and treated 4 hours at 600°C . Three nanocrystals with different orientations are visible: $d_{311} = 0.253$ nm, $d_{220} = 0.296$ nm, $d_{111} = 0.480$ nm.

	Precursors	P (bar)	T (°C)
TiO₂	bis(ammonium lactato)titanium dihydroxide (ALT: Aldrich) : 50 % in mass in water	300	300
Fe₂CoO₄	Co(NO ₃) ₂ 0.025 mol/L Fe(NO ₃) ₃ 0.05 mol/L NaOH 0.25mol/L	300	440
BaZrO₃	ZrO(NO ₃) ₂ , 6H ₂ O 0.075 mol/L Ba(NO ₃) ₂ 0.3 mol/L NaOH 2 mol/L	350	500


Table 1

	S_{BET} (m^2/g)	Phase	EDXS	a (\AA)	ϕ_{XRD} (nm)	Hc (Oe) at 77K
TiO₂	255 ± 2	anatase	-	-	3 ± 1	-
Fe₂CoO₄	236 ± 2	spinel	Fe/Co = 2.04	-	3 ± 1	3730
Fe₂CoO₄ treated (4 hours at 600°C)	15.4 ± 0.1	spinel	Fe/Co = 2.03	8.3839 ± 0.0001	34 ± 1	7350
BaZrO₃	9.75 ± 0.1	perovskite	Ba/Zr = 0.98	4.198 ± 0.001	74 ± 1	-

Table 2

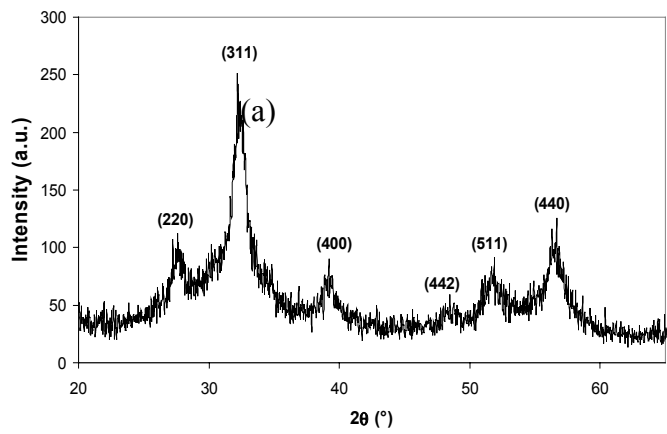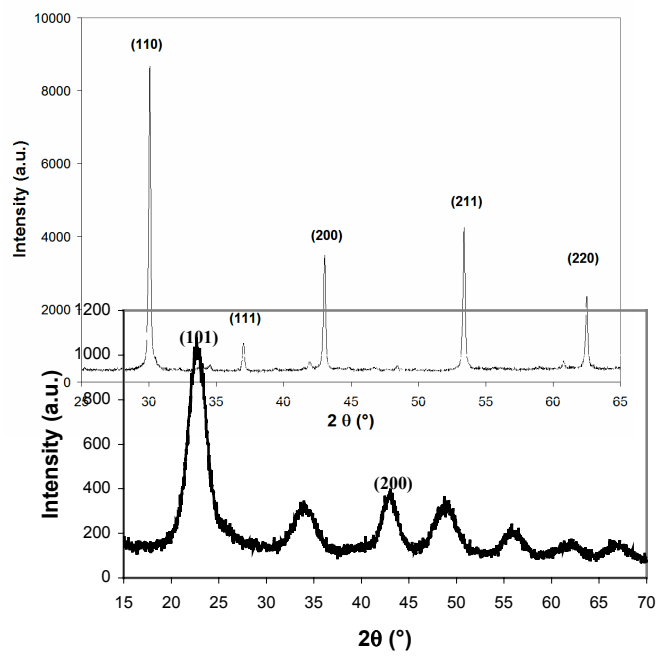

(b)

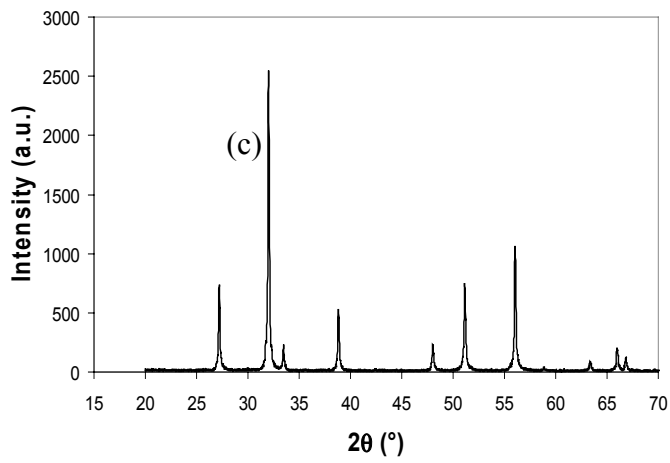

(d)

Fig.1

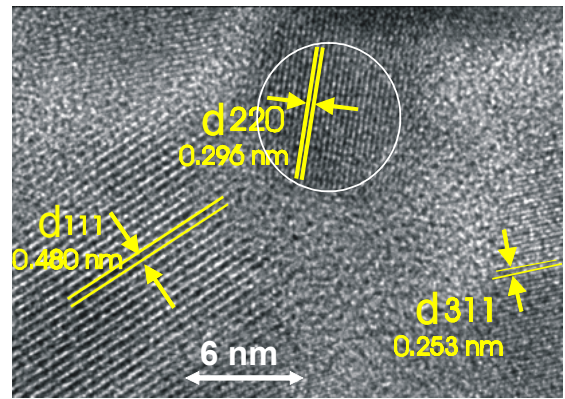
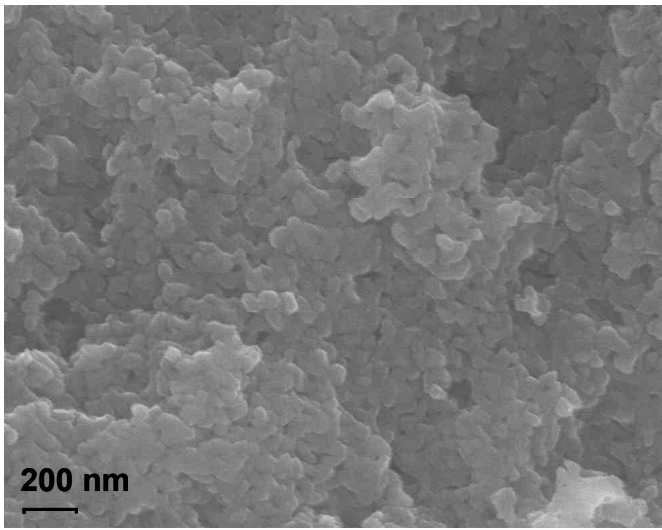


Fig. 2

-
- [i] Hahn, H.W.; Tannenbaum, R.; Feldheim, D.L.; Kubiak, C. P.; Siegel, R. W.; Editors. "Synthesis, Functional Properties and Applications of Nanostructures" (Proceedings of a Symposium held 17-20 April 2001 in San Francisco, California.) [In: Mater. Res. Soc. Symp. Proc., 2002; 676] (2002).
- [ii] Millot, N., Aymes, D., Bernard, F., Niepce, J.C., Traverse, A., Bourée, F., Cheng, B.L. & Perriat, P., *J. Phys. Chem. B*, 2003, **107**, 5751.
- [iii] Millot, N., Bégin-Colin, S., Champion, Y., Hÿtch, M. J., Le Caër, G. & Perriat, P., *J. Solid State Chem.*, 2003, **170**, 30.
- [iv] Guigue-Millot, N., Champion, Y., Hÿtch, M.J., Bernard, F., Bégin-Colin, S., Perriat, P., *J. Phys. Chem. B*, 2001, **105** (29), 7125.
- [v] N. Millot, N. Keller, P. Perriat, *Phys.Rev. B*, 2001, **64**, 012402.
- [vi] N. Millot, O. Tillement, P. Perriat, *Phys. Rev. B*, 2003, **68**,113405.
- [vii] Aymes, D., XIN, B., NIEPCE, J.C., Proceedings "De la poudre au matériau massif", Albi, France, June 3-5 (2003).
- [viii] Darr, J.A., Poliakoff, M., *Chem.Rev.*, 1999, **99**, 495.
- [ix] Adschiri, T., Kanazawa, K., Arai, K., *J. Amer. Ceram. Soc.*, 1992, **75**, 1019.
- [x] Millot, N., Xin, B., Heintz, O., Jausse, C., Aymes, D., to be submitted to *J. Solid State Chemistry*.
- [xi] Langford, J. I., *National Institute of Standards and Technology*, Special Publication, 1992, **846**, 145.
- [xii] Möckel, H., Giersig, M., Willig, F., *J. of Materials Chemistry*, 1999, **9**, 3051.
- [xiii] Malats I Riera, A., Pourroy, G., Poix, P., *J. Solid State Chem.*, 1992, **101**, 195.
- [xiv] P. Poix, F. Basile, C. Djega-Mariadassou, *Ann. Chim.* **3**, 159 (1975).

[xv] Kolen'ko, Y.V.; Burukhin, A.A.; Churagulov, B.R.; Oleinikov, N.N.; Vanetsev, A.S.,
Inorganic Materials (Translation of Neorganicheskie Materialy), 2002, **38**(3), 252-255.

[xvi] Maschio, S., Bachiurrini, A., Lucchini, Elio and Brückner, S., *J. European Cer. Soc.*,
2004, **24**, 2241-2246.