

Effect of V₂O₅ on The Sintering Behaviour, Cation Order and Properties of Ba₃Co_{0.7}Zn_{0.3}Nb₂O₉ Ceramics

F. Azough, C. Leach and R. Freer
Manchester Materials Science Centre, UMIST & University of Manchester,
Manchester, M1 7HS, UK

Keywords: Microwave dielectrics, complex perovskites, Ba₃Co_{0.7}Zn_{0.3}Nb₂O₉

Abstract.

The microstructures and microwave dielectric properties of barium cobalt zinc niobate ceramics prepared by conventional mixed oxide route have been investigated. It was found that low levels doping of V₂O₅ (up to 0.2 wt%) can significantly improve densification of the specimens and their properties. Dielectric properties of V₂O₅ doped samples were affected by 1:2 ordering in the B-site. Slow cooling after sintering or annealing in a nitrogen atmosphere improved the unloaded quality factor (Q.f values) significantly. The Ba₃Co_{0.7}Zn_{0.3}Nb₂O₉ (BCZN) ceramics exhibited $\epsilon_r=34.5$, $\tau_f=0$ ppm/C and Q.f=85000 at 4GHz.

Introduction.

Ceramic dielectrics have been extensively used for microwave communication systems. The advantage of using microwave dielectric ceramics is the size reduction of microwave components. Requirements for these dielectric materials must be the combined dielectric properties of a high dielectric constant (ϵ_r), low dielectric loss (high Q.f value) and a near-zero temperature coefficient of resonant frequency(τ_f). These three parameters are related to the size, frequency selectivity and temperature stability of the system, respectively. To satisfy the demands of microwave circuit designs, each dielectric property should be precisely controlled. Several complex perovskites ceramics A(B'_{1/3}B''_{2/3})O₃ are been known for their excellent microwave dielectric properties. Among these materials, Ba₃Co_{0.7}Zn_{0.3}Nb₂O₉ possesses a high dielectric constant ($\epsilon_r \sim 34.5$), a high quality factor (Q.f 56000 to 85000 GHz) and small temperature coefficient of resonant frequency ($\tau_f \sim 0$)[1,2,3].

In this study we investigate the effect of V_2O_5 on the sintering behaviour, cation order and microwave dielectric properties, particularly the Q.f values of $Ba_3Co_{0.7}Zn_{0.3}Nb_2O_9$ ceramics.

Experimental.

Specimens were prepared by a conventional mixed oxide route. High purity (>99.9%) $BaCO_3$, ZnO , Nb_2O_5 and V_2O_5 were used as raw materials. The powders were weighed according to the composition $Ba_3Co_{0.7}Zn_{0.3}Nb_2O_9 + 7.5 \text{ wt}\%Ba_8Zn_1Nb_6O_{24}$. They were mixed in propan-2-ol with zirconia media for 18h, calcined at 1100°C for 4h, then V_2O_5 was added and wet milled for 18h and dried. Pellets were formed by pressing powders in steel dies (20mm diameter) at a pressure of 100MPa. These were sintered at 1450° for 4h in air and cooled at $60^\circ\text{C}/\text{hour}$. Selected compositions were annealed in a nitrogen atmosphere at 1360°C for up to 10 hours.. The final dimensions of these specimens were approximately 15.5mm diameter and 9mm thick.

Microstructural observation of the sintered ceramics was performed by means of SEM (Philips XL30). The sintered surfaces of ceramics were ground (to 1200 grade SiC) and polished (to $1\mu\text{m}$ diamond paste). The samples were then coated with carbon prior to SEM analysis.

The crystal structures were examined by XRD (Philips Analytical, X'pert-MPD) employing $\text{CuK}_{\alpha 1}$ radiation under the conditions 50kV and 40mA. The samples were scanned at 0.04° intervals of 2θ in the range $10-70^\circ$; the scan rate was $0.01^\circ 2\theta/\text{sec}$.

TEM specimens were prepared from the sintered ceramics, after lapping and polishing to form 3mm diameter discs. The discs were dimpled to $30\mu\text{m}$ thickness in the centre and then thinned to electron transparency with a Gatan Precision Ion Polishing System. The specimens were investigated using a Tecnai G2 TEM operating at 300kV.

The dielectric properties were measured by the parallel plate method[4]. The τ_f measurements were performed using a silver plated aluminium cavity at temperatures between -10 and $+60^\circ\text{C}$.

Results.

Figure 1 shows the bulk densities of BCZN ceramics. It can be seen that the addition of V_2O_5 promoted densification. A similar trend was observed (Figure 2) for the Q.f values of the samples. Figure 3 shows the XRD spectrum of samples prepared with 0.025 wt% V_2O_5 . The pattern shows the characteristics of a 1:2 ordered hexagonal structure with the presence of the superstructure reflection at $2\theta = 17.6^\circ$. An extra peak were observed at $2\theta = 29.6^\circ$ which is associated with the formation of the $\text{Ba}_8\text{Zn}_1\text{Nb}_6\text{O}_{24}$ phase.

The increase in the Q.f values is a result of the combined effect of the increase in density, structural homogenisation at atomic levels and Zn, Co and Nb ordering on the B-sites. These changes have been achieved by a liquid phase mechanism through the additions of vanadium oxide.

The dielectric constants and τ_f values of the dense samples were not significantly affected by V_2O_5 additions and were ~ 34.5 and ~ 0 ppm/ $^\circ\text{C}$ respectively. Further enhancement of the quality factor of the ceramics was achieved by annealing in a nitrogen atmosphere at temperatures below the order-disorder transition (Figure 4). XRD examinations showed that The increase in the degree of B-site ordering is the main factor for the enhancement in the Q.f values.

The formation of the $\text{Ba}_8\text{Zn}_1\text{Nb}_6\text{O}_{24}$ phase was confirmed by SEM and TEM examination. Figure 5 shows bright field TEM image of the above sample. The $\text{Ba}_8\text{Zn}_1\text{Nb}_6\text{O}_{24}$ phase appeared as elongated needle shape grains in the microstructure. The presence of structural modulations can be seen in the grains of this phase. This phase was observed at the grain

boundaries as well as within BCZN grains. Figure 6 shows a high resolution TEM image of a single domain. The grain is viewed along $\langle 011 \rangle$ type zone axis of the cubic unit cell.

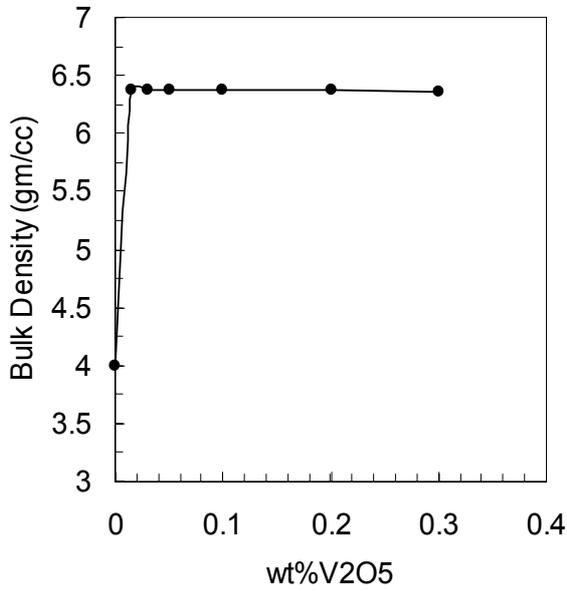


Figure 1. Bulk densities of BCZN ceramics as a function of V_2O_5 content.

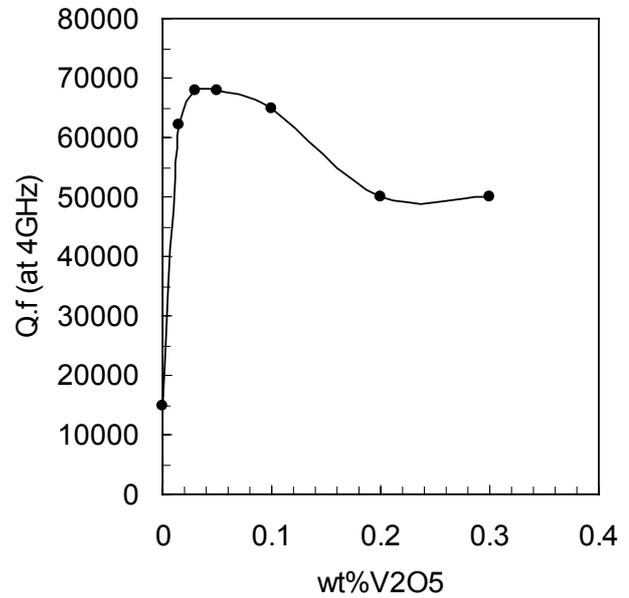


Figure 2. Q.f values of BCZN ceramics as a function of V_2O_5 content.

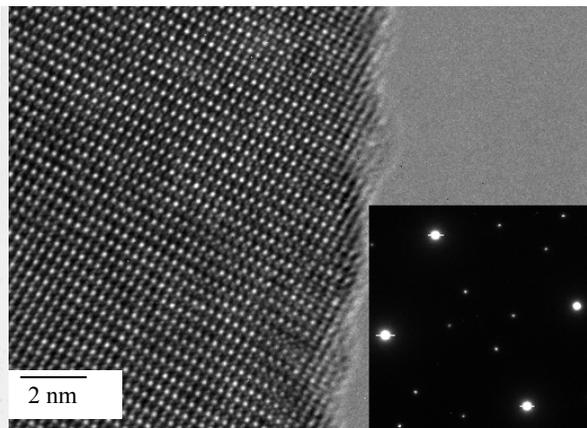
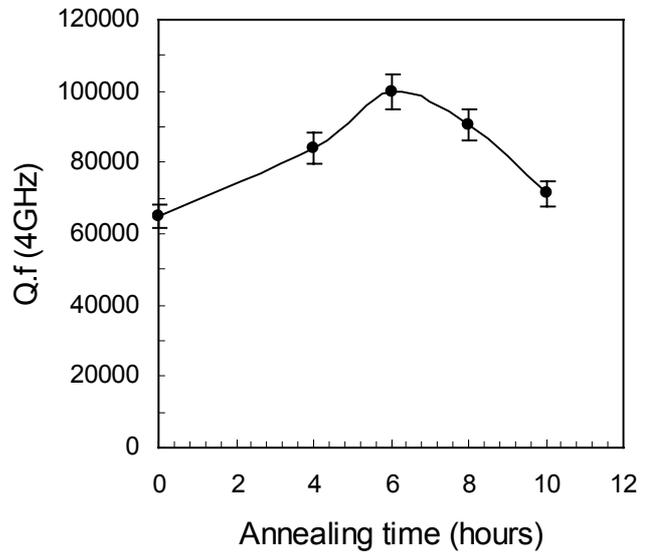
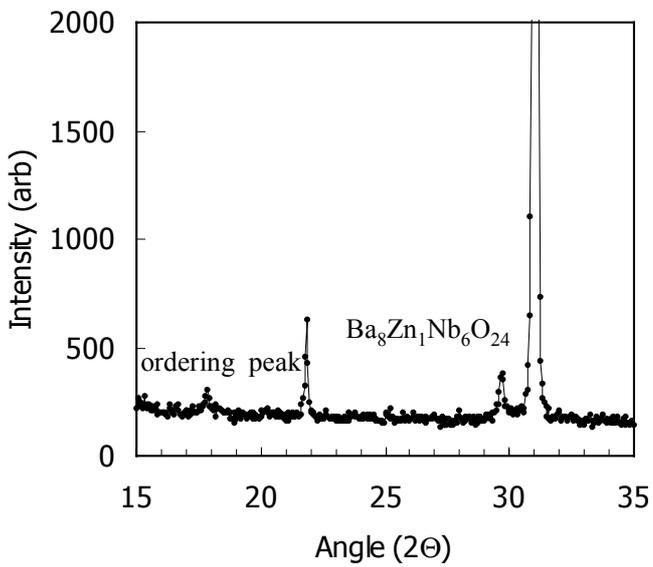


Figure 5. TEM image of BCZN ceramic.

Figure 6. High resolution TEM image of BCZN ceramic.

Conclusions.

High density with a high degree of 1:2 order in BCZN ceramics were achieved by additions of vanadium oxide. BCZN ceramics prepared with 0.025 wt% V₂O₅ addition sintered at 1450°C for 4 hours and annealed in nitrogen atmosphere possessed excellent microwave dielectric properties: $\epsilon_r \sim 34.5$, Q.f value ~ 85000 at 4GHz and τ_f of close to zero.

Acknowledgements.

The financial support of EPSRC through GRR72655/01 and the assistance of Filtronic Ltd with microwave measurements are gratefully acknowledged.

References.

1. Endo. K, Fujimoto. K, Murakawa. K, Dielectric properties of ceramics in Ba(Co_{1/3}Nb_{2/3})O₃-Ba(Zn_{1/3}Nb_{2/3})O₃ solid solutions, *J. Am. Ceram. Soc.*, 1987, **70**[9], C-215-C-218.
2. Ahn. C-W, Jang, H-J, Nahm. S, Park, H-m, Lee. H-J, Effect of microstructure on the microwave dielectric properties of Ba(Co_{1/3}Nb_{2/3})O₃ and (1-x)Ba(Co_{1/3}Nb_{2/3})O₃-xBa(Zn_{1/3}Nb_{2/3})O₃ solid solutions, *J. Europ. Ceram. Soc.*, 2003, **23**, 2473-2478.
3. Azough. F, Leach, C. Freer, R. The effect of additives and processing parameters on the microstructure and microwave dielectric properties of Ba(Me_{1/3}Nb_{2/3})O₃ complex perovskites (Me= Zn, Co, Ni and Mg), presented at the *Microwave materials and their applications meeting (MMA20002)*, Poster 23, 1-3 September, 2002, York, UK.
4. Hakki. B.W, and Coleman, P. D., A dielectric resonator method of measuring inductive capacitance in the millimetre range , *IEEE Trans. Microwave Theory Thec.*, 1980, MTT-**18**, 402-410.